

DEVELOPMENT OF NEW CASTING MAGNESIUM-BASED ALLOYS WITH INCREASED MECHANICAL PROPERTIES (p. 4–10)

Vadim Shalomeev, Eduard Tsvirco, Yuri Vnukov,
Yekaterina Osadchaya, Spartak Makovskyi

Influence of a number of alloying elements (Nd, Ge, Si, Y, Sc, Zr, Ti and Hf) on structure formation, room-temperature mechanical properties and high-temperature strength of ML5 magnesium alloy have been studied.

Influence of the alloying elements on a shape and size of intermetallic compounds has been established. A quantitative and qualitative analysis of the intermetallic phase in additionally alloyed ML5 have been made, its influence on the structure, room-temperature mechanical properties and high-temperature strength of magnesium castings has been investigated.

Influence of morphological and topological features of the structure constituents of the magnesium alloys on their properties has been established. It was shown that micro alloying of the magnesium alloys within a range of 0.05–0.1 % wt. results in an increase of the intermetallic compound volume percent by ~ 1.5 times, reducing their size with simultaneous formation of spherical intermetallic compounds located in the grain centre and serving as additional solidification nuclei. It was found out that at the volume fraction of the intermetallic compounds within a range of 0.35–0.45 % a maximum ductility of the magnesium alloy is attained. Further increase of the intermetallic compound amount leads to decrease in the ductility due to their excessive precipitation and greater strengthening of the metal.

Introduction of the studied magnesium alloys ensures a higher level of room-temperature mechanical properties and a high-temperature strength of the castings that makes them a good candidate material to be used in newly developed machines and assemblies.

Keywords: magnesium alloy, alloying elements, structure, intermetallic compounds, mechanical properties, high-temperature strength.

References

- Ovchynnykov, A. V. (2012). Prymenenye tytanovykh splavov s SMK strukturoi dlia vosstanovleniya detalei rotornoj chasty HTD. *Avtomaticheskaja svarka*, 2 (706), 21–25.
- Bohuslaev, V. A., Kachan, A. Ya., Kalynyna, N. E. (2009). Avyatsyonno-kosmicheskye materyali y tekhnolohyy. Izd-vo OAO «Motor Sych», 351.
- Rourke, D. J. (2000). Magnesium-current status and future prospects. *Magnesium New Business Opportunities*, 14–23.
- Son, K. E., Kanh, M. Ch., Kym, K. Kh. (2006). Yssledovaniya y razrabotky prymereniya mahnyevikh splavov v Yuzhnoi Koree. *Lyteinoe proyzvodstvo*, 1, 8–10.
- Dyrynha, X., Maier, P., Fekner, D., Bolen, P. (2006). Nastoiashchee y budushchee mahnyevikh splavov v nashei tsyvylyzatsyy. *Lyteinoe proyzvodstvo*, 1, 4–7.
- Kornylov, Y. Y. (1961). *Fyzyko-khymicheskye osnovy zharoprochnosti splavov*. Moscow: AN SSSR, 214.
- Ospov, K. A. (1960). *Voprosy teoryi zharoprochnosti metallov y splavov*. Moscow: AN SSSR, 323.
- Yum-Rozery (1959). *Struktura metallov y splavov*. Moscow: Metallurhyzat, 391.
- Darken, L. S. (1960). *Fyzicheskaia khymia metallov*. Moscow: Metallurhyzat, 245.
- Hshneidner, K. A. (1965). *Splavy redkozemelnykh metallov*. Moscow: Mir, 185.
- Uobber, Dzh. (1962). *Metallurhiya i metallovedeniye plutyoniya i eho splavov*. Moscow: Hosatomyzdat, 102.
- Horonovskiy, Y. T. (1987). *Kratkyi spravochnik po khymyy*. Kyiv: Naukova dumka, 829.
- Hryhorovych, V. K. (1969). *Zharoprochnost i dyahrammy sostoiannya*. Moscow: Metallurhiya, 323.
- Wang, T., Zhu, T., Sun, J., Wu, R., Zhang, M. (2015). Influence of rolling directions on microstructure, mechanical properties and anisotropy of Mg-5Li-1Al-0.5Y alloy. *Journal of Magnesium and Alloys*, 3 (4), 345–351. doi: 10.1016/j.jma.2015.11.001
- Jia, H., Feng, X., Yang, Y. (2015). Influence of solution treatment on microstructure, mechanical and corrosion properties of Mg-4Zn alloy. *Journal of Magnesium and Alloys*, 3 (3), 247–252. doi: 10.1016/j.jma.2015.08.006
- Li, C. Q., Xu, D. K., Zu, T. T., Han, E. H., Wang, L. (2015). Effect of temperature on the mechanical abnormality of the quasicrystal reinforced Mg – 4 % Li – 6 % Zn – 1.2 % Y alloy. *Journal of Magnesium and Alloys*, 3 (2), 106–111. doi: 10.1016/j.jma.2015.02.003
- Chen, J., Sun, Y., Zhang, J., Cheng, W., Niu, X., Xu, C. (2015). Effects of Ti addition on the microstructure and mechanical properties of Mg-Zn-Zr-Ca alloys. *Journal of Magnesium and Alloys*, 3 (2), 121–126. doi: 10.1016/j.jma.2015.05.001
- Chen, H. L., Lin, L., Mao, P. L., Liu, Z. (2015). Phase stability, electronic, elastic and thermodynamic properties of Al-RE intermetallics in Mg-Al-RE alloy: A first principles study. *Journal of Magnesium and Alloys*, 3 (3), 197–202. doi: 10.1016/j.jma.2015.08.003
- Kai, W. (2015). Effect of microstructure evolution on mechanical property of extruded Mg-12Gd-2Er-1Zn-0.6Zr alloys. *Journal of Magnesium and Alloys*, 1, 23–28.
- Shalomeev, V. A., Tsyvirko, E. I., Lukinov, V. V., Lysenko, N. O. (2009). Pat. 39357 Ukraina: MPK S22S 23/00. Lyvarnyi splav na osnovi mahniui z pidvyshchenoiu ridynotekuchistiu. Zaiavtyel y patentoobladatel Zaporozhskiy natsyonalnii tekhnicheskyy unyversytet; declared: 28.08.08; published: 25.02.09, Biul. 4.
- Shalomeev, V. A., Tsyvirko, E. I., Lukinov, V. V., Lysenko, N. O., Parkhomenko, A. V. (2009). Pat. 39358 Ukraina: MPK S22S 23/00. Lyvarnyi splav na osnov mahniui. Zaiavtyel y patentoobladatel Zaporozhskiy natsyonalnii tekhnicheskyy unyversytet; declared: 28.08.08; published: 25.02.09, Biul. 4.

DETERMINATION OF RATIONAL ROUGHNES OF THE SIDE SURFACE OF THE RAIL TOP IN CURVED SECTIONS OF THE UNDERGROUND RAILWAY TRACK (p. 11–17)

Serhii Voronin, Oleksii Skoryk, Yevhen Korostelov

This work provides a series of studies are aimed at determining the forces acting in the contact «wheel-rail» in curvilinear sections of the underground railway track.

To define the dependence of the friction coefficient on the parameters of microgeometry of contact surfaces, the technique of laboratory tests on a friction machine was developed. The laboratory tests were carried out on the friction machine by testing specially made models, whose material directly and size in conversion corresponds to the components of the contact «wheel-rail». In order to determine parameters

of force impact on model samples, calculation of contact voltages, which occur in the real contact under conditions of unlubricated friction and their conversion into the «modeling» contact were performed.

As a result of testing, rational values of the friction coefficient and wear rate of the contact «wheel-rail» at unlubricated friction under conditions of contacting in curvilinear sections of the underground railway track were defined.

The obtained values of parameters of microgeometry of contacting surfaces under conditions of their practical implementation can significantly reduce the wear rate in the contact «wheel-rail» in curvilinear sections of the underground railway track. In turn, the decrease in wear rate will lead to the decrease in costs on maintenance of the underground railway track.

Keywords: contact voltages, model samples, rational roughness, «wheel-rail», underground railway track.

References

- Shtompel, A., Skoryk, O., Ovchinnikov, O. (2014). Problema rivnoresursnosti elementiv verkhnoyi budovy bezstykovoyi koliyi. *Sbornyk nauchnykh trudov SWorld*, 3 (36), 64–69.
- Wang, W. J., Lewis, R., Yang, B., Guo, L. C., Liu, Q. Y., Zhu, M. H. (2016). Wear and damage transitions of wheel and rail materials under various contact conditions. *Wear*, 362–363, 146–152. doi: 10.1016/j.wear.2016.05.021
- Santamaria, J., Vadiello, E. G., Oyarzabal, O. (2009). Wheel-rail wear index prediction considering multiple contact patches. *Wear*, 267 (5-8), 1100–1104. doi: 10.1016/j.wear.2008.12.040
- Ignesti, M., Malvezzi M., Marini, L., Meli, E., Rindi, A. (2012). Development of a wear model for the prediction of wheel and rail profile evolution in railway systems. *Wear*, 284-285, 1–17. doi: 10.1016/j.wear.2012.01.020
- Alonso, A., Giménez, J. G. (2008). Wheel-rail contact: Roughness, heat generation and conforming contact influence. *Tribology International*, 41 (8), 755–768. doi: 10.1016/j.triboint.2008.01.004
- Remington, P., Webb, J. (1996). Estimation of wheel/rail interaction forces in the contact area due to roughness. *Journal of Sound and Vibration*, 193 (1), 83–102. doi: 10.1006/jsvi.1996.0249
- Rovira, A., Roda, A., Marshall, M. B., Brunskill, H., Lewis, R. (2011). Experimental and numerical modelling of wheel-rail contact and wear. *Wear*, 271 (5-6), 911–924. doi: 10.1016/j.wear.2011.03.024
- Voronyn, S., Korostev, E. (2014). Analiz sushchestvuyushchykh sposobov umensheniya bokovoho yznosa relsov v pare trenyya «koleso-rels» v kryvukh uchastkakh puty. *Informatsiyno-keruyuchi systemy na zaliznychnomu transporti*, 3, 22–27.
- Chen, H., Namura, A., Ishida, M., Nakahara, T. (2016). Influence of axle load on wheel/rail adhesion under wet conditions in consideration of running speed and surface roughness. *Wear*. doi: 10.1016/j.wear.2016.05.012
- Aharkov, O., Yosyfovich, R. (2015). Vyznachennya kontaktynykh napruzhen v reykhakh typu P50, yaki ekspluatuyutsya v metropoliteni. *Nauka ta prohres transportu Visnyk Dnipropetrovs'koho natsional'noho universytetu zaliznychnoho transportu*, 4 (58), 71–86.
- Keropyan, A., Gorbayuk, S. (2016). Impact of Roughness of Interacting Surfaces of the Wheel-Rail Pair on the Coefficient of Friction in their Contact Area. *Procedia Engineering*, 150, 406–410. doi: 10.1016/j.proeng.2016.06.753
- Yvanov, Y. A. (2010). Otsenka vozmozhnostey protsessov vosstanovleniya profilya poverkhnosti kolesnykh par. *Visnyk Skhidnoukrayinskoho natsionalnoho universytetu imeni V. Dalya*, 10 (152), 72–78.
- Budyukyn, A. M. (2009). Vybory rezhyma vreznoyu shlyfovanyia kolesnoy staly. *Konstruktysionno-tekhnologicheskoe obespechenye nadezhnosti koles relsovykh ekypazhey*, 89–93.
- Potapov, D., Vitolberh, V. (2006). Systema shlifuvannya reyok v koliyi reykoshlifuvalnym poyezdnyy z aktyvnymy robochymy orhanamy na zaliznytsyakh Ukrainy. *Informatsiyno-keruyuchi systemy na zaliznychnomu transporti*, 5, 6, 70–73.
- Voronyn, S., Karpenko, S., Korostelov, E. (2014). Modelirovaniye kontakta «koleso-rels» po bokovoy poverkhnosti puty na mashyne trenya. *Zbirnyk naukovykh prats UkrDAZT*, 148, 201–204.
- Krahelsky, Y. V. (1977). *Osnovy raschetov na trenye y yznos*. Moscow: Mashynostroenye, 526.
- Krahelsky, Y. V. (1968). *Trenye y yznos*. Moscow: Mashynostroenye, 480.
- Danilenko, E. (2010). *Zaliznychna koliya. Ulashtuvannya, proektuvannya y rozrakhunky, vzyemodiya z rukhomym skladom*. Vol. 2. Kyiv: Inpres, 457.
- Belyaev, N. M. (1965). *Soprotivlenye materialov*. Moscow: Nauka, 856.
- Shakhunants, H. (1987). *Zheleznodorozhnyy put*. 3rd edition. Moscow: Transport, 479.
- Albrekht, V. H., Smyrnov, M. P., Shul'ha, V. Ya. et. al.; Amelyn, S. V., Yakovleva, T. H. (Eds.) (1990). *Osnovy ustroystva y raschetov zheleznodorozhnogo puty*. Moscow: Transport, 367.
- Yakovlev, V. (1967). *Yssledovaniye kontaktnykh napryazheniy v elementakh kolesa y relsa pry deystviy vertykalnykh y kasatelnnykh syl*. *Trudy LYYZHT*, 187, 3–89.
- Krahelsky, Y., Alysyn, V. (1978). *Trenye yznashyvaniye y smazka*. Moscow: Mashynostroenye, 400.
- Sosnovskiy, L. (2003). *Osnovy trybofotyky*. Part 1. Homel: BelHUT, 246.

VISCOSITY EVALUATION OF THE MIXTURE OF COAL TARS FROM COLLECTION MAIN AND PRIMARY COOLER ON THE BASE OF RHEOMETER MEASUREMENTS AND EMPIRICAL FORMULAS (p. 17–23)

Alexander Pasternak, Leonid Bannikov, Anna Smirnova

Viscosity of heavy and light coal tars from the coking process of coal blends with a decreasing portion of Ukrainian coal was measured. In addition, measurement of viscosity of mixtures of coal tar was carried out. Concentration of mixture met the standards of the regulations of the washing liquids for gas space of primary cooler. The temperature dependence of the viscosity of the tar mixture was evaluated according to some empirical equations. In particular, the equations have been used considering deviations from the ideal state. The viscosity of the individual samples of heavy and light tars was not appropriately investigated. This also applies to the temperature dependence. This is common practice for coal tar viscosity measurements in Engler units. Also, there are no empirical relationships; we cannot predict the viscosity of the tar when mixed, as we do for the petroleum oil matter. Anomalous decline in viscosity with the addition of 5–20 % light tar that corresponded to the minimum activation energy of viscous flow was revealed experimentally.

Keywords: mixture viscosity, empirical relationship, coal tar, gas collecting main, primary cooler.

References

- Gogoleva, T., Shustikov, V. (1992). Chemistry and technology of processing of coal tar. Moscow: Metallurgy, 256.
- Kaufman, A., Kharlampovich, G. (2005). Technology of coke production. *Ye: VUHIN NCA*, 288.

3. Kryachuk, V., Olchov, V., Lutokhin, N., Ekhaus, V. (2006). The primary cooling of coke oven gas. Its purification from tar and naphthalene on electrostatic precipitators. *Coke and Chemistry*, 12, 19–21.
4. Bannikov, L., Shustikov, V., Pasternak, A., Skripchenko, N., Kleshnya, G. (2015). Coal tar and coke oven gas condensate emulsion formation, physical and chemical properties, ways of use and destruction intensification. *Journal of Coal Chemistry*, 3, 37–43.
5. Bannikov, L., Pasternak, A., Pokhylko, A., Pilipenko, V. (2015). Emulsion rheological behavior for gaseous phase of primary coke oven gas cooler. *Coke and Chemistry*, 8, 27–32.
6. Schramm, G. (2003). *Bases practical rheology and rheometry*. Moscow: KolosS, 312.
7. Krasulia, M., Shustikov, V. (1991). Influence of the composition on the viscosity of the coal tar. *Chemistry of solid fuel*, 3, 77–81.
8. Hugaboom, D. A., Powers, S. E. (2002). Recovery of Coal Tar and Creosote from Porous Media: The Influence of Wettability. *Ground Water Monitor Remediation*, 22 (4), 83–90. doi: 10.1111/j.1745-6592.2002.tb00774.x
9. Scholes, G. C., Gerhard, J. I., Grant, G. P., Major, D. W., Vidumsky, J. E., Switzer, C., Torero, J. L. (2015). Smoldering Remediation of Coal-Tar-Contaminated Soil: Pilot Field Tests of STAR. *Environmental Science & Technology*, 49 (24), 14334–14342. doi: 10.1021/acs.est.5b03177
10. Maloka, I. E., Hashim, E. T., Hasaballah, A. A. (2004). A Correlation for Temperature Effect on Coal Tar Pitches and Refined Tars Viscosity. *Petroleum Science and Technology*, 22 (11-12), 1427–1433. doi: 10.1081/lft-200027830
11. Shi, Q., Zhang Z., Cao, X., Gu, K. (2014). Measuring and analyzing on viscosity-temperature characteristic of high temperature coal tar. *Journal of China Coal Society*, 9 (11), 2335–2339.
12. Cui, D., Xu, C., Chung, K. H., Shi, Q. (2015). Potential of Using Coal Tar as a Quenching Agent for Coal Gasification. *Energy Fuels*, 29 (11), 6964–6969. doi: 10.1021/acs.energyfuels.5b01524
13. Yu, P., Fang, M., Tang, W., Luo, Z. (2013). Viscosity reduction of coal tar from fluidized bed pyrolysis. *J Fuel Chem Technol.*, 41 (01), 26–32.
14. Zhmud, B. (2014). Viscosity blending equations. *Lube Magazine*, 06, 24–29.
15. Fletcher, T. H., Kerstein, A. R., Pugmire, R. J., Solum, M. S., Grant, D. M. (1992). Chemical percolation model for devolatilization. 3. Direct use of carbon-13 NMR data to predict effects of coal type. *Energy Fuels*, 6 (4), 414–431. doi: 10.1021/ef00034a011
16. Pyshyev, S., Grytsenko, Y., Bilushchak, H., Pyshyeva, R., Danyliv, N. (2015). Production of Indene-coumarone Resins as Bitumen Modifiers. *Petroleum and Coal Petroleum and Coal*, 57, 303–314.

INFLUENCE OF THE NATURE OF BOUNDARY LUBRICATING LAYERS ON ADHESION COMPONENT OF FRICTION COEFFICIENT UNDER ROLLING CONDITIONS (p. 24–31)

Oksana Mikosyanchyk, Rudolf Mnatsakanov,
Aleksandr Zaporozhets, Ruslan Kostynik

The patterns of the change in antifriction properties of contact due to strength characteristics of boundary films of physical and chemisorbed nature were examined. The purpose of the study was to establish the influence of lubricating and rheological properties of the boundary films, formed on the surface layers of metal activated by friction, on the kinetics of change in the friction coefficient. The method of estimation

of tribotechnical properties of contact under non-stationary conditions with cutting off the lubricant feed to the friction zone was used. Its essence is in determining the period of the setting of contact surfaces and registration of lubricating, antifriction and rheological indicators in this period.

An increase in antifriction properties of contact during pure rolling was established, owing to localization of tangential shear stresses in the liquid phase of a lubricant film; an increase in the friction coefficient is caused by an increase in tangential shear stresses of the boundary structured chemisorption films during transition to rolling with slippage.

The influence of slippage between the contact surfaces was analyzed, the increase in which from 3 % to 40 % leads to acceleration of the period of occurrence of the first signs of the setting, which is manifested by an increase in the adhesive component of the friction coefficient during desorption of boundary layers. During the setting of friction pairs, an abrupt periodic decrease in the friction coefficient was established and the manifestation of hydrodynamic effects in contact during melting of boundary layers was observed. The results of the studies may be used for designing the friction pairs of machines and mechanisms, which operate under non-stationary conditions (variable speeds, loads and temperature).

Keywords: friction coefficient, shear stress, effective viscosity, slippage, boundary films of lubricant.

References

1. Zaporozhets, V. V. (1980). Dinamicheskie karakteristiki prochnosti poverhnostnykh sloev i ih otsenka. *Trenie i iznos*, 1 (4), 602–609.
2. Buckley, D. H. (1981). Surface effects in adhesion, friction, wear, and lubrication / *Tribology Series 5*. Elsevier Science, New York, NY, 630.
3. Heuberger, M., Luengo, G., Israelachvili, J. (1997). Topographic Information from Multiple Beam Interferometry in the Surface Forces Apparatus. *Langmuir*, 13 (14), 3839–3848. doi: 10.1021/la960942a
4. Luengo, G., Israelachvili, J., Granick, S. (1996). Generalized effects in confined fluids: new friction map for boundary lubrication. *Wear*, 200 (1-2), 328–335. doi: 10.1016/s0043-1648(96)07248-1
5. Rice, J. R., Sammis, C. G., Parsons, R. (2005). Off-Fault Secondary Failure Induced by a Dynamic Slip Pulse. *Bulletin of the Seismological Society of America*, 95 (1), 109–134. doi: 10.1785/0120030166
6. Offner, G., Knaus, O. (2015). A Generic Friction Model for Radial Slider Bearing Simulation Considering Elastic and Plastic Deformation. *Lubricants*, 3 (3), 522–538. doi: 10.3390/lubricants3030522
7. Wang, Y., Wei, B., Wu, X. (2012). Wet Friction-Elements Boundary Friction Mechanism and Friction Coefficient Prediction. *Tribology in Industry*, 34 (4), 198–205.
8. Garg, H. C., Kumar, V., Sharda, H. B. (2009). Thermohydrostatic analysis of capillary compensated symmetric hole-entry hybrid journal bearing operating with non-Newtonian lubricant. *Ind Lubrication and Tribology*, 61 (1), 11–21. doi: 10.1108/00368790910929485
9. Muhortov, I. V., Usoltsev, N. A., Zadorozhnaya, E. A., Levakov, I. G. (2010). Usovershenstvovannaya model reologicheskikh svoystv granichnogo sloya smazki. *Trenie i smazka v mashinakh i mekhanizmakh*, 5, 8–19.
10. Shram, V. G., Kovalskiy, B. I., Bezborodov, Yu. N. et. al. (2012). Issledovanie vliyaniya produktov temperaturnoy destruktivnoy i nagruzki na protivoznosnye svoystva chastichno sinteticheskogo motornogo masla TNK Super 5w-40SL/CF. Chast 2. *Vestnik KuzGTU*, 6 (94), 67–74.

11. Kovalskiy, B. I., Kovalskiy, S. B., Berko, A. V., Malyisheva, N. N. (2010). Rezultaty ispytaniya mineralnogo motor-nogo masla na temperaturnuyu stoykost. *Izvestiya Tomskogo politehnicheskogo universiteta*, 316 (2), 46–50.
12. Korotkevich, S. V., Martynenko, S. M., Kravchenko, V. V., Paramonov, M. V. (2004). Samoorganizatsiya smazochnykh sloev pri granichnom trenii. *Vestnik GGTU im. P. O. Suhogo*, 4 (17), 13–16.
13. Pravednikov, I. S. (2005). Kontaktnoe vzaimodeystvie tverdyykh tel s uchetom davleniya, temperatury i tverdosti. *Electronic scientific journal «Oil and Gas Business»*, 1. Available at: <http://ogbus.ru/article/kontaktnoe-vzaimodeystvie-tverdykh-tel-s-uchetom-davleniya-temperatury-i-tverdosti/>
14. Ognjanovic, M. (2004). Progressive Gear Teeth Wear and Failure Probability Modeling. *Journal of the Serbian Tribology Society*, 26 (3&4), 44–49.
15. Mikosyanchyk, O. O. (2014). Patent na korysnu model #88748, MPK G 01 N 3/56 Prystrij dlya ocinky trybotekhnichnykh xarakterystyk tryboelementiv. u 2013 13450, declared: 19.11.13; published: 25.03.14, Byul. 6, 4.
16. Rayko, M. V. (1974). Issledovanie smazochnogo deystviya neftnykh masel v usloviyakh raboty zubchatykh peredach. Kyiv: KIIGA, 369.
17. Ahmatov, A. S. (1967). *Molekulyarnaya fizika granichnogo treniya*. Moscow: Fizmatgiz, 472.
18. Porohov, V. S. (1983). *Tribologicheskie metody ispytaniya masel i prisadok*. Moscow: Mashinostroyeniye, 183.
19. Kragelskiy, I. V., Alisin, V. V. (Eds.) (1978). *Trenie, iznashivanie i smazka: Spravochnik*. Kn. 1. Moscow: Mashinostroyeniye, 400.
20. Voronin, S. V., Stefanov, V. O. (2014). The research of tribological characteristics of smectic layer of boundary film. *Problems of Tribology*, 2 (72), 58–64.
21. Yanzhong, W., Bin, W., Xiangyu, W. (2012). Wet Friction-Elements Boundary Friction Mechanism and Friction Coefficient Prediction. *Tribology in Industry*, 34 (4), 198–205.
22. Gurskiy, B. E., Chichinadze, A. V. (2007). Teplovaya zadacha treniya i ee razvitiye. Chast 2. Rol teplovykh yavleniy v razrushenii zubchatykh koles tsilindricheskikh evolventnykh peredach realnykh razmerov. *Trenie i iznos*, 4 (28), 418–425.
23. Klamann, D. K. (1988). *Smazki i rodstvennyye produkty*. Himiya, 488.
24. Thompson, P. A., Robbins, M. O. (1990). Origin of Stick-Slip Motion in Boundary Lubrication. *Science*, 250 (4982), 792–794. doi: 10.1126/science.250.4982.792
25. Robbins, M. O., Thompson, P. A. (1991). Critical Velocity of Stick-Slip Motion. *Science*, 253 (5022), 916. doi: 10.1126/science.253.5022.916
26. Lemaître, A., Carlson, J. (2004). Boundary lubrication with a glassy interface. *Physical Review E*, 69 (6). doi: 10.1103/physreve.69.061611
27. Popov, V. L. (2001). Termodinamika i kinetika plavleniya sdvigom tonkogo sloya smazki, zaklyuchennogo mezhdu tverdymi telami. *Zhurnal tekhnicheskoy fiziki*, 71 (5), 100–110.
28. Lemaître, A. (2002). Rearrangements and Dilatancy for Sheared Dense Materials. *Physical Review Letters*, 89 (19). doi: 10.1103/physrevlett.89.195503

DETERMINING PARAMETERS OF ELECTRIC DRIVE OF A SLEEPER-TYPE TURNOUT BASED ON ELECTROMAGNET AND LINEAR INDUCTOR ELECTRIC MOTOR (p. 32–41)

Serhii Buriakovskiy, Artem Maslii, Andrii Maslii

As a result of the conducted study, we determined parameters of the electric drive of a sleeper-type turnout based on the linear electromagnetic energy converters.

By parameters of the electric drive we mean not only the design of a linear electric motor, such as diameters of stator, anchor, their length, the magnitude of air gap, the type of coil, but also availability of additional elements. In this case — availability of the springs that ensure the required force at the motion start. In this case, two variants of the linear motors design were considered and various layouts of electric drive of a turnout, respectively. In both cases, the force from the motor is transmitted directly to the coupling rod between the rail points, which makes it possible to exclude such an additional element as the reducer, which has a relatively low performance efficiency, additional metal consumption and overall size, which also decreases general reliability of the device as a whole. The problem of multicriterion optimization of parameters of electric motors was compiled. Geometric dimensions of the drives were accepted as the variable parameters. The analysis revealed that the best result in the search for global optimum out of 11 variants were demonstrated by the Weyl method (with the mean-square deviation of 680.9N for electromagnet) and the method of cyclic minimum (with the mean-square deviation of 1052.3N for induction motor). The estimation was performed according to results of the optimal (minimal) value of the mean-square deviation of electromagnetic force from the resistance force. As the load we used the 1/22 type of a turnout with the maximum weight of rail points for the P65 rail. The data of the study are necessary for creating a new class of electric drives of the turnouts, which make it possible to increase the performance efficiency of the device, as well as its performance speed and, in doing so, to contribute to fulfillment of the program of implementation of high-speed traffic in Ukraine. As a result of the studies, it was found that it is expedient to use the proposed systems of electromagnetic energy converters as the new type of source of mechanical energy in the turnout.

Keywords: turnout, electric drive, linear induction motor, electromagnet, methods of optimization.

References

1. Maslyi, Ar. S., Buriakovskiy, S. H., Petrushyn, A. D., Maslyi, An. S. (2013). Razrabotka elektropriyoda strochno-ho perevoda s ventylno-ynduktornym elektrodvyhatel'em y yssledovanye na matematicheskoi modeli rezhymov eho raboty. *Visnyk Natsionalnoho tekhnichnogo universytetu «KhPI»*, 36, 198–201.
2. Smyrnov, V. V., Buriakovskiy, S. G. (2010). Rehulyruemyi strochnyi elektropriyod. *Mizhnarodnyi informatsii nauko-vo-tekhnichnyi zhurnal «Lokomotyv-inform»*, 7, 8–9.
3. Kornienko, V. V., Omel'yanenko, V. I. (2007). Vy'sokoskorostnoy e'lektricheskij transport. *Mirovoj opyt. Nacional'ny'j tekhnicheskij universitet «Khar'kovskij politekhnicheskij institut»*, 159.
4. Lyubars'kiy, B. G., Yeritsian, B. Kh., Yakunin, D. I., Hliebova, M. L. (2015). Optyimizatsiya parametrv liniinoh dvyhuna nakhylu kuzova transportnykh zasobiv. *Visnyk Natsionalnoho tekhnichnogo universytetu «KhPI»*, 41, 58–66.
5. Hovorukha, V. V. (2008). Proektyrovanye y vnedrenye strochnikh perevodov dlia hornikh predpriyatiy. *Sbornyk Donetskoho Natsionalnoho tekhnicheskoho unyversyteta*, 16 (142), 57–66.
6. Kondratenko, S. L. (2011). Avtoperekliuchatel strochnoho elektropriyoda. *Avtomatyka y telemekhanika zheleznikh doroh Rossyy. Tekhnika, tekhnolohiya, sertyfikatsiya*, 1, 114–119.

7. EBI Switch 2000. Available at: <http://www.bombardier.com/content/dam/Websites/bombardiercom/supporting-documents/Sustainability/Reports/BT/Bombardier-Transportation-EPD-EBI-Switch-2000-en.pdf>
8. Liudvinavičius, L., Dailydka, S., Ślaskowski, A. (2016). New possibilities of railway traffic control systems. *Transport Problems*, 11 (2), 133–142. doi: 10.20858/tp.2016.11.2.13
9. Wang, P. Design of High-Speed Railway Turnouts. Available at: <http://www.sciencedirect.com/science/book//9780323396172?via%3Dihub>
10. Zharinova, A. G. Pat. 95497 Ukrainy: MPK(2014.01) B61L 5/00. Elektropryvid strilochnogo perevodu. Zayavnyky ta patentovlasnyky Buryakovskij S. G., Maslij A. S., Maslij A. S. # u201407676; declared: 08.07.14; published: 25.12.14, Byul. 24, 4.
11. Poliakov, V. O., Khachapuridze, M. M. (2007). Analysis and synthesis of the dynamics of electrodynamic trains with linear motor. *Nauka ta progres transportu*, 15, 159–166.
12. Alonge, F., Cirrincione, M., D'Ippolito, F., Pucci, M., Sferlaza, A. (2016). Adaptive feedback linearizing control of linear induction motor considering the end-effects. *Control Engineering Practice*, 55, 116–126. doi: 10.1016/j.conengprac.2016.06.018
13. Ganji, B., Askari, M. H. (2016). Analysis and modeling of different topologies for linear switched reluctance motor using finite element method. *Alexandria Engineering Journal*, 5. doi: 10.1016/j.aej.2016.07.017
14. Yvanchenko, F. K., Krasnoshapka, V. A. (1983). *Dynamyka metallurhycheskykh mashyn*. Moscow: Metallurhiya, 295.
15. Buriakovskiy, S. H., Smyrnov, V. V. (2008). Matematycheskaia model elektropryvoda strelochnogo perevoda s uchetchom kharakterystyky treniya. *Visnyk natsionalnoho tekhnichnoho universytetu «Kharkivskiy politekhnichnyi institut»*, 30, 329–330.
16. Altaev, V. Y., Motoryn, V. Y. (1986). *Optymyzatsiya v tekhnike*. Moscow: Myr, 350.
17. Reznikov, Y. M. (1975). *Strelochnye elektropryvody elektrycheskoi y horochnoi tsentralyzatsyy*. Moscow: Transport, 152.
18. Shtoiar, R. (1992). *Mnookryterialnaia optymyzatsiya*. Moscow: Radio y sviaz, 504.
19. Weise, T. (2008). *Global optimization algorithms theory and application*. E-Book, 820.
20. Severyn, V. P. (2013). *Metodi mnohomernoi bezuslovnoi mynymyzatsyy*. Nacional'nyj tekhnicheskij universitet «Khar'kovskij politekhnicheskij institut», 160.

THE IMPACT OF AN UNEVEN LOADING OF A BELT CONVEYOR ON THE LOADING OF DRIVE MOTORS AND ENERGY CONSUMPTION IN TRANSPORTATION (p. 42–51)

Anatoly Semchenko, Mykola Stadnik, Pavlo Belitsky,
Dmytro Semchenko, Olena Stepanenko

The object of the present study is the process of transporting the mined bulk by a belt conveyor during intensive coal mining. The subject of the study is the impact of uneven load flow patterns on the energy parameters of transportation and the resource of the belt conveyor during heavy mining of coal. The aim of the study is to assess the impact of the weight of the load that is transported by a conveyor belt on the drive motors loading and energy consumption during intensive coal mining. The research is performed through a statistical analysis of experimental results obtained by the Dongiprovuglemach institute (Ukraine) regarding the load flow and the capacity of the belt conveyor 2LU120V used by the mine Dovzhanska-Capital (Sverdlovsk, Ukraine).

The capacities of drive motors were considered through a regression analysis. A correlational and spectral analysis was applied to consider the load flow, the load weight, and the capacities of the drive motors. The study has specified the estimated drag coefficient in the movement of the conveyor belt under conditions of intensive mining of coal. Specific energy consumption for transporting the mined bulk by the conveyor was estimated regarding the loading of the belt. The work was done to assess the effect of the size and type of the load flow and the load weight on energy consumption and the resource of the conveyor and to justify a further increase of the technical level of belt conveyors. The results show substantial irregularities in the load flow and the transported load weight, their impact on the amount and type of an uneven loading of the drive motors, and specific energy consumption for transportation and the conveyor resource.

The study has shown that if the loading is small a bigger load is imposed on the drive motor that is located in the place of the belt running off the drive; if the load is big, a bigger load is imposed on the drive motor that is located in the place of the belt running onto the drive. The main dispersion of the load flow occurs at low frequencies corresponding to the duration of the technological cycle of extracting and transporting coal. When the modes of the conveyor operation are close to the maximum load of the belt, energy is least of all consumed for transporting the load. If the loading is reduced, there is a hyperbolic increase in specific energy consumption for transportation. The drag coefficient of the conveyor belt movement, obtained by the experiment data on the capacity value of the idly running conveyor, is significantly higher than the value that is suggested by the method of a technological calculation of the process. This factor should be taken into account while determining the capacity of a drive and calculating the traction of the machine. The results can be used for creating belt conveyors within mining systems of an improved technical level for highly efficient intensive coal mining.

Keywords: intensification of coal mining, conveyor, load flow, load weight, energy consumption.

References

1. Nikolaichuk, V., Budishevsky, V., Gutarevich, V., Kislun, V., Sulima, A.; Budishevsky, V. A., Sulima, A. A. (Eds.) (2003). *Transportable and Technological logistics in energy-intensive industries*. Donetsk.
2. Adadurov, V., Arinenkov, V., Voyush, F. et al.; Budishevsky, V. A., Sulima, A. A. (Eds.) (1999). *Theoretical basis and calculations of transport in energy-intensive industries*. Donetsk, 217.
3. Shahmeyer, L., Dmitriev, V., Lobacheva, A. (1972). *The dynamics of traffic and speed control of conveyor belts*. Moscow: Nedra, 173.
4. Lobacheva, A. (1971). *Energy performance of conveyor transport and irregular with adjustable-speed*. Mining and quarrying transport, 158–163.
5. Babockin, G., Shprekher, D. (2007). *Mathematical model of the twin-engine conveyor with adjustable electric*. Proceedings of the V International (16th All-Russian) Conference on automated electric, 365–366.
6. Korneev, S., Dobronogova, V., Safonov, V. (2012). *Emergency overload of downhole scraper conveyors with hydrodynamic drive and hydraulic tensioning devices simulation*. Collection of scientific works of Donbass State Technical University, 36, 35–43.

7. Osichev, A., Tkachenko, A. (2008). Assessing the impact of the internal viscous friction of the traction body and scraper conveyor resistance forces its movement the dynamics of electromechanical system. *Bulletin of National Technical University KhPI*, 30, 187–189.
8. Osichev, A., Tkachenko, A. (2008). The development of the family computer models to study dynamical processes in electric conveyors. *News M.O. strogadsky Kremenchug sovereign politechnical university*, 3 (50), Part 2, 154–157.
9. Osichev, A., Tkachenko, A. (2009). Evaluation of the dynamic properties of the electric scraper conveyor SR 72 at various reasons for jamming its working body. *Problems automated electric. Theory and Practice*, 516.
10. Zaklika, M., Kolek, M., Tytko, S. Belt conveyors with adjustable speed. Available at: <http://www.bartec-russia.ru/files/mining/for-conveyance.pdf>
11. Ivantsov, V. Energy-saving soft starter and regulation of the conveyor speed. Available at: <http://www.erasib.ru/articles/conveyor-eraton-fr>
12. Lauhoff, H. (2006). Is the speed of belt conveyors regulation contributes to energy savings? *Glukauf*, 1, 9–16.
13. Wheeler, C. A. (2008). *Evolutionary Belt Conveyor Design – Optimizing Coasts. Bulk Material Handling by Conveyor Belt*. 7, Littleton, Colorado, 108.
14. Prokuda, V., Mishansky, Yu., Protsenko, S. (2012). Research and evaluation of freight traffic on the main conveyor transport the CAP «Mine «Pavlogradska». Public company DTEK «Pavlogradugol» Mining electrician, 88, 107–111.
15. Kondrakhin, V., Stadnik, N., Belitskii, P. (2013). Traffic measurement on the belt conveyor through removable tensor device with belt tension accounting. *DonNTU scientific works, electromechanical series*, 1, 79–87.
16. Kondrahin, V., Stadnik, N., Belitskii, P. (2013). Operating parameters statistical analysis for the belt conveyor in mine. *DonNTU scientific works, electromechanical series*, 2, 140–150.

DETERMINING EXPERIMENTALLY THE STRESS-STRAINED STATE IN THE RADIAL ROTARY METHOD OF OBTAINING WHEELS RIMS (p. 52–60)

**Ruslan Puzyr, Tetiana Haikova,
Oleg Trotsko, Roman Argat**

Questions of experimental study regarding the stress-strained state in the radial rotary method of producing the steel rims of wheels are examined. The physical simulation of the process of profiling the rims is performed on the installation, designed especially for these purposes. The models of the narrow-profile and wide-profile rims of wheels were tested. The grids method was applied for conducting the experiments. The obtained information was processed by the methods of mathematical statistics and probability theory. The results of experimental data made it possible to arrive at a conclusion about the most dangerous sections of the profiles of the rims of wheels, which, in the process of deformation, obtain compressive radial deformations, which confirms the studies conducted previously. The largest deformations occur in the places of radius couplings of the profile, deformations increase from one transition to the next and their total magnitude can exceed the permitted by 20 % of the initial thickness of the workpiece. No essential difference between the two schemes of profiling the rims of wheels was revealed.

Keywords: profiling, wheel rim, plastic deformation, stress-strained state, experiment, intensity of stresses, resource of plasticity.

References

1. Wang, X., Li, L., Deng, L., Jin, J., Hu, Y. (2015). Effect of forming parameters on sheet metal stability during a rotary forming process for rim thickening. *Journal of Materials Processing Technology*, 223, 262–273. doi: 10.1016/j.jmatprotec.2015.04.009
2. Jin, J., Wang, X., Li, L. (2016). A sheet blank rotary forging process for disk-like parts with thickened rims. *Journal of Mechanical Science and Technology*, 30 (6), 2723–2729. doi: 10.1007/s12206-016-0534-6
3. Bi, D. S., Yang, G., Chu, L., Zhang, J., Wang, Z. H. (2011). Numerical Simulation on Spinning Forming Process of Automotive Wheel Rim. *Materials Science Forum*, 704–705, 1458–1464. doi: 10.4028/www.scientific.net/msf.704-705.1458
4. Dragobetskij, V., Zjukov, A., Konovalenko, A. (2005). Uchet vlijaniya izmenenija tolshhiny listovoj zagotovki v processe deformirovaniya. *Visnik Kremenchuc'kogo derzhavnogo politechnichnogo universitetu: Naukovi praci KDPU*, 2, 61–62.
5. Potekushin, N. (1977). Jeksperimental'noe issledovanie processa formoobrazovaniya profilirovannyh obod'ev. *Avtomobil'naja promyshlennost'*, 1, 33–36.
6. Currie, A. (2000). Finite Element Analysis of an Automotive Wheel. A Case Study, National Conference Publication. Australia: Institution of Mechanical Engineers, 16–20.
7. Conceição Antonio, C. A., Trigo Barbosa, J., Simas Dinis, L. (2000). Optimal design of beam reinforced composite structures under elasto-plastic loading conditions. *Structural and Multidisciplinary Optimization*, 19 (1), 50–63. doi: 10.1007/s001580050085
8. Ray, G. S., Sinha, B. K. (1992). Profile optimization of variable thickness rotating disc. *Computers & Structures*, 42 (5), 809–813. doi: 10.1016/0045-7949(92)90191-2
9. Mori, K., Osakada, K. (1982). Simulation of three dimensional rolling by the rigid-plastic finite element method. Numerical methods in industrial forming processes: proc. International Conf. Swansea (UK): Pineridge Press, 747–756.
10. Kasatkin, B., Kudrin, A., Lobanov, L. (1981). Jeksperimental'nye metody issledovaniya deformacij i naprjazhenij. Kyiv: Naukova dumka, 583.
11. Ogorodnikov, V. A., Grushko, A. V., Gucaljuk, A. V. (2014). Vybory kriteriev deformiruемости pri ocenke ispol'zovannogo resursa plastichnosti v processah obrabotki metallov davleniem. *Visnik NTU «HPI»*, 43, 127–136.
12. Romanovskij, V. (1979). *Spravochnik po holodnoj shtampovke*. Leningrad: Mashinostroenie. Leningrad: otd-nie, 520.
13. Tret'jakov, A., Zjuzin, V. (1973). *Mechanicheskie svojstva stalej i splavov pri obrabotke davleniem*. Moscow: Metallurgija, 224.
14. Glushhenkov, V. (2010). *Uprochnenie metallov v obrabotke metallov davleniem*. Samara: SGAU, 33.
15. Puzyr, R., Savelov, D., Argat, R., Chernish, A. (2015). Distribution analysis of stresses across the stretching edge of die body and bending radius of deforming roll during profiling and drawing of cylindrical workpiece. *Metallurgical and Mining Industry*, 1, 27–32.
16. Puzyr, R. (2015). Raschet komponent tenzora naprjazhenij na radiuse zakruglenija profilirujushhego rolka pri izgotovlenii oboda kolesa. *Obrabotka materialov davleniem*, 2, 192–195.
17. Savelov, D., Dragobetsky, V., Puzyr, R., Markevych, A. (2015). Peculiarities of vibrational press dynamics with hard-elastic restraints in the working regime of metal powders molding. *Metallurgical and Mining Industry*, 2, 67–75.

UDC 621.314.26:622.647.2

DOI: 10.15587/1729-4061.2016.75936

Об'єктом дослідження є процес транспортування гірничої маси стрічковим конвеєром при інтенсивному вуглевидобутку. Предмет дослідження — закономірності впливу нерівномірності вантажопотоку на енергетичні параметри транспортування і ресурс стрічкового конвеєра в умовах інтенсивного вуглевидобутку. Встановлено суттєву нерівномірність вантажопотоку, маси вантажу, що транспортується, та їх вплив на величину і характер нерівномірності навантаженості двигунів приводу, а також питомі енерговитрати на транспортування і ресурс конвеєра. Використання отриманих результатів сприятиме створенню шахтних стрічкових конвеєрів для високоефективного інтенсивного вуглевидобутку

Ключові слова: інтенсифікація вуглевидобутку, конвеєр, вантажопотік, маса вантажу, енерговитрати

Объектом исследования являются процессы транспортирования горной массы ленточным конвейером при интенсивной угледобыче. Предмет исследования — закономерности влияния неравномерности грузопотока на энергетические параметры транспортирования и ресурс ленточного конвейера в условиях интенсивной угледобычи. Установлена существенная неравномерность грузопотока, массы транспортируемого груза на ленте и их влияние на величину и характер неравномерности нагруженности двигателей привода, а также удельные энергозатраты на транспортирование и ресурс конвейера. Использование полученных результатов будет способствовать созданию шахтных конвейеров для высокоэффективной интенсивной угледобычи

Ключевые слова: интенсификация угледобычи, конвейер, грузопоток, масса груза, энергозатраты

THE IMPACT OF AN UNEVEN LOADING OF A BELT CONVEYOR ON THE LOADING OF DRIVE MOTORS AND ENERGY CONSUMPTION IN TRANSPORTATION

A. Semenchenko

Doctor of technical sciences, Professor*

E-mail: aksemen@inbox.ru

M. Stadnik

Doctor of technical sciences, Professor

Department of electrical systems and automation technology in the agricultural sector

Vinnitsia National Agricultural University

Sonyachna str., 3, Vinnitsa, Ukraine, 21008

E-mail: stadnik1948@gmail.com

P. Belitsky

Postgraduate student*

E-mail: dcb80@mail.ru

D. Semenchenko

PhD, assistant professor*

E-mail: sda190476@mail.ru

O. Stepanenko

PhD, Assistant Professor*

E-mail: elena_step85@mail.ru

*Department of mining machines and mechatronic systems of mechanical engineering

Donetsk national technical university

Shybankova sq., 2, Krasnoarmiysk, Ukraine, 85300

1. Introduction

One of the directions in developing modern coal mines is intensification of coal mining in order to improve productivity and reduce the cost of mining. This causes a decrease in the number and an increase in the length of mine faces, improving the performance and power capacity of the involved machines. A significant role in intensifying coal mining is played by underground transport the costs of which can exceed 40 % of the cost of production. Therefore, it is important to increase the efficiency of the transportation means of a mining enterprise [1].

Currently, belt conveyors are one of the most important links in the transport system of coal mines. Belt conveyors are characterized by flexibility, high performance at a great length and a relatively low transport capacity, smooth and quiet running, ease of automation, a possibility to create assembly lines, including branched lines, low metal content, a possibility to transport people, etc. [2]. Thus, improving the efficiency and the technical level of belt conveyors is an important part of intensifying coal mining at mining enterprises.

One of the ways to increase the efficiency of conveyor transport is to reduce the cost of transporting the mined

bulk [3]. The present study is devoted to finding ways to reduce energy costs and to increase the conveyor resource at variable load flows by determining the patterns of influence of an uneven load weight on these parameters as well as by obtaining source data for designing highly efficient mine transport. It is important to reduce energy consumption and to improve the conveyor resource in order to reduce production costs. Even when the cost of mining raw materials is reduced by 5 % at an average annual production rate of 6 million tonnes of coal and the cost of UAH 1.5 thousand per tonne, it is possible to achieve an annual economic benefit of UAH 450 million.

2. Literature review and problem statement

The most universal indicator of energy efficiency of a transport unit is the parameter of specific energy consumption E that denotes energy consumption for transporting 1 tonne of a load by a belt across a distance of 1 km, which is determined by the formula:

$$E = \frac{N}{Q_{av}L} \text{ kW} \cdot \text{h} / (\text{t} \cdot \text{km}), \quad (1)$$

where N is energy consumption, kW; Q_{av} is the average load flow, t/h; L is the length of the conveyor, km.

In real conditions, the amount of the consumed energy and the average load flow corresponding to the current value of the load weight on the conveyor change during the operation of the transport machinery. For a proper evaluation of specific energy consumption for transporting the load by an underground conveyor belt, it is reasonable to use data obtained in representative conditions of mines having modern treatment and tunnel complexes.

The dependence of energy consumption for transporting loads by conveyor belts on the load flow has been researched since the second half of the 1960s [4]. The studies have been based on the results of a chronometry monitoring of the process of loading coal into mine trolleys of a trunkline transport. The considered sources of load flows have been the cutter-loaders 1K-52Sh, MK-64, and LGD-1 as well as the plough units USB-2M. Since these machines are now out of production, it is necessary to conduct further research on the characteristics of mine flows generated by modern high-performance cutter-loaders and road headers.

It should be noted that even if it has been proven that scraper conveyors require speed regulation [5–9] the question of the advisability and a rational algorithm of the drawbar organ speed control is still insufficiently studied for belt conveyors to ensure, as a rule, transportation of loads under an intensive extraction of coal from multiple faces. Contemporary researchers of this problem provide various results on evaluating energy efficiency of belt conveyors with variable drives [10–13]. There is also a problem with the assessment of the statistical characteristics of load flows in mine conveyor transport that directly determine the result of calculating their energy efficiency and resource, including the result for mine belt conveyors with variable drives [14].

Currently, there are no sufficient experimental data on the energy characteristics of modern belt conveyors of mines equipped with high-performance extraction com-

plexes. Obtaining and further accumulation of data of experimental studies of load flows and energy performance of conveyor transport while using these systems can be the way to increase the efficiency of their use and to intensify production.

3. The aim and tasks of the study

The aim of the study is to determine the influence of the conveyor belt loading on the loading of its drive, energy consumption and the conveyor resource to create a highly efficient mine transport for intensive extraction of coal.

To achieve the goal, it is necessary to solve the following tasks:

- to evaluate the dynamism of loading the drive motor, which characterizes the capacity of the belt conveyor;
- to determine the uneven rate of the mined bulk and its impact on the workload of the belt, the influence of the latter on the capacity developed by the drive motors of the belt conveyor as well as energy performance in an idle mode and load transportation;
- to clarify experimentally the drag factor of the belt movement in representative conditions of intensive mining;
- to use the results of experimental studies to make recommendations for maintaining a constant load of the conveyor belt along the whole length and in terms of the receiving capacity.

4. Research materials and methods

4.1. The experimental setup

Assessment of the energy performance of the conveyor was carried out on the basis of the results of experimental studies of load flows and the drive capacity conducted by the Dongiprovuglemach institute (Ukraine) for the belt conveyor 2LU120V (No. 4) of the eastern conveyor line of the Dovzhanska-Capital mine of the LLC DTEK Sverdlovanthracite (Sverdlovsk, Ukraine). The eastern conveyor line transports the mined bulk of two working faces equipped with the complexes MKD80 and MKD90 and one preparatory face. The parameters are the following: the conveyor length is $L=730$ m, the belt speed is $v=2$ m/s, the rated capacity of the drive is $N_{dr}=2 \times 250=500$ kW, the maximum capacity is $Q_{max}=1500$ t/h, the belt is 2RTLO2500, the transportation angle is $\beta=3^\circ$, and the transportation is from top to bottom. The capacity developed by the motors is measured at their input terminals. The load volume was assessed by the readings of a removable tensiometer located in the upper branch of the conveyor unloading boom. The conveyor is equipped with a tight winchdown tensioner.

The flowchart of the experimental procedure is shown in Fig. 1. The results of the experimental data obtained in 2013 and 2014 are presented in [15, 16]. They reflect the obtained arrays of current load values on the tensiometric bearing Q and the consumed energy N . The experiment duration is $T=17$ hours, with the readings interval $\Delta t=1$ s and the number of readings $k=3600T/(\Delta t)=61,200$ s.

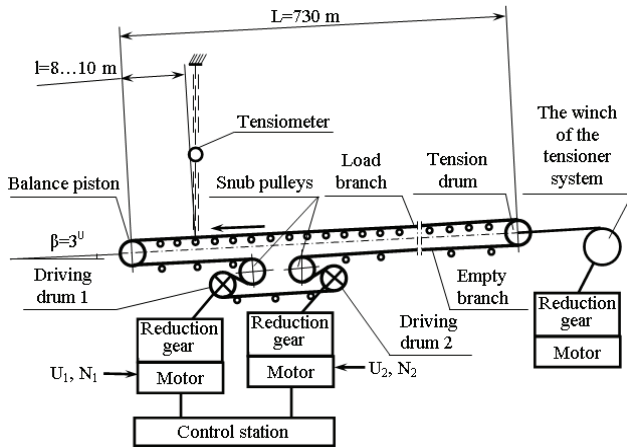


Fig. 1. The flowchart of experimental studies of the capacity developed by the drive motors for the conveyor 2LU120V (No. 4) of the eastern conveyor line of the Dovzhanska-Capital mine of the LLC DTEK Sverdlovanthracite (Sverdlovsk, Ukraine): L is the transportation length, l is the distance from the balance piston axis to the point of the installed sensors on the balance console, Q is the load flow, v is the belt speed, U₁ and U₂ are the voltage volumes applied to the drive motors D₁ and D₂, whereas N₁ and N₂ are the capacities developed by the drive motors D₁ and D₂

4. 2. The methodology and procedure of the study

The weight of the load placed on the conveyor belt at a moment of time t:

$$W(t) = \int_{t'=t+t_1}^{t+t_1+t_2} Q(t')dt, t, \quad (2)$$

where t₁ and t₂ are time indicators of the load passing from the place of weighing it up and the loading place to the place of unloading, respectively; Q(t') is the current experimental value of the load flow.

The value of the transported load on the conveyor belt at the current time is:

$$W(t_i) = 0.001 \sum_{k=i+6}^{i+371} Q_k, \quad i \in [4...((3.600T/(\Delta t) - 365)], t, \quad (3)$$

where Q_k is the value of the load weight on the tensiometer roll bearing at the time t_k = k · Δt, kg/s.

The nature of the changes in the capacities N₁ and N₂ developed by the drive motors and determined in experimental studies and their respective load weights W on the conveyor according to the dependence (3) is shown in Fig. 2. The analysis of the curves reveals a significant effect of the weight of the transported load on the capacities developed by the drive motors. In the cases of idling and load transportation, the capacity of one drive motor of a belt conveyor ranges from 70 kW to 180 kW, and its value depends on the weight value of the load transported by the conveyor. The start-up power that is developed by the drive motors amounts to 380 kW.

In order to determine the type of the electric drive motors loading and the dependence of the capacities developed by them on the weight of the transported load, the capacities developed by the drive motors were registered in experimental trials and subjected to a regression analysis. To select

the optimal mode of the belt conveyor drive, specific energy consumption for transporting 1 tonne of the load was determined for a distance of 1 km at a varying weight of the load transported on the belt. Data were specified for calculating the traction of the belt conveyor according to the standard procedure.

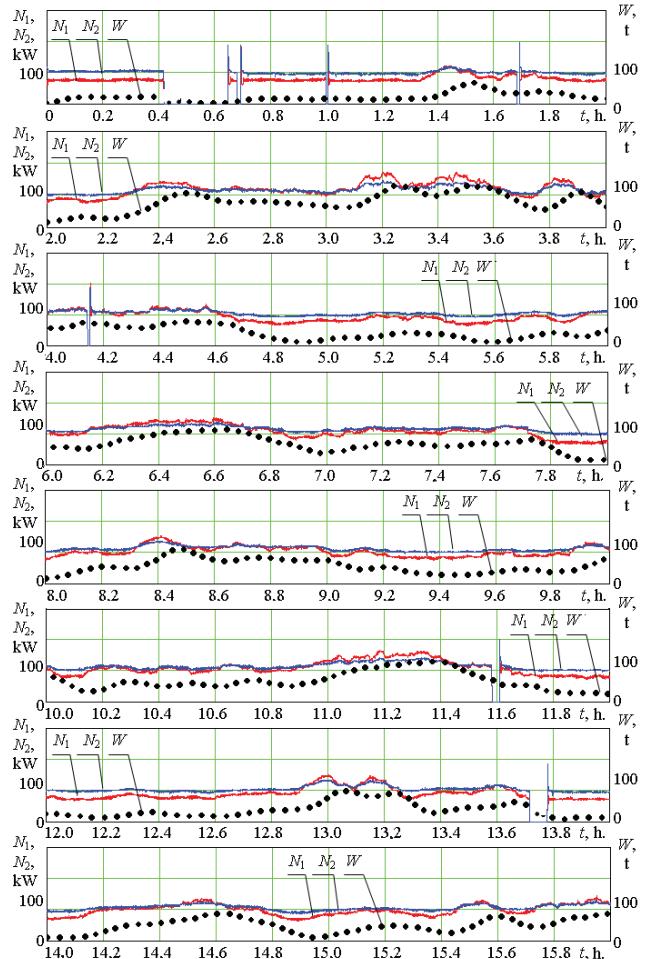


Fig. 2. Changes in the capacity of the drive motors N₁ (the red line) and N₂ (the blue line) and the weight W of the load on the belt (the black marker) at a long-term operation of the belt conveyor 2LU120V of the eastern conveyor line of the Dovzhanska-Capital mine

5. The results of the experiment to establish the influence of the unevenness of the load flow and the belt loading on the drive loading

The regression dependence of the conveyor system capacity on the load weight on the belt is the following [16]:

$$N_i = N_0 + \Delta N_W \cdot W_i \text{ kW}, \quad (4)$$

where N₀ = 160 kW is the capacity of an idle conveyor, kW; ΔN_W = 1.1 kW/t is the increment of the consumed capacity at increasing the weight of the load on the belt by 1 tonne.

The uneven loading of the electric motors in terms of their capacity is determined by the ratio factor of the capacities of the drive motors D₁ and D₂, and, respectively, N₁ and N₂, which vary over time:

$$K_{Ni} = \frac{N_{1i}}{N_{2i}}. \quad (6)$$

Fig. 3 shows the behaviour of the changing capacities N_1 and N_2 developed by the drive motors of the belt conveyor 2LU120V. The characteristic curves reveal a significant effect of the transported load weight on the type of loading the drive motors. When the weight of the load transported by the conveyor is equal to $W=70$ tonnes, the conveyor drive motors are loaded uniformly, with $K_N=1$. When the weight of the load transported by the conveyor is $W<70$ tonnes, the drive motor D_2 is loaded more than D_1 , and when $W>70$ tonnes, it is less loaded than the motor D_1 . To quantify the unevenness, there is a mutual positioning of the capacity values of N_1 and N_2 of the drive motors depending on the transported load weight (Fig. 4), and the point cloud and the graph show a linear regression dependence of the capacity ratio of the drive motors K_N depending on the relative conveyor loading (Fig. 5). The relative loading of the conveyor $W/W_{\max} = 1$ corresponds to the full load of the drawbar element of the machine along the length of the transportation and the receiving capacity, where the value of $W_{\max} = 126$ m indicates the maximum possible transportable load weight by the conveyor 2LU120V functioning in representative mine conditions along the length and in terms of the receiving capacity.

The following linear regression equations were obtained according to the results of the statistical processing of the dependencies of the low frequency component of the capacity developed by the drive motors D_1 and D_2 and the factor of their capacity dependence on the weight of the load transported by the belt — $N_1(W)$, $N_2(W)$, and $K_N(W)$, respectively:

$$N_{ji} = N_{jxi} + \Delta N_{ji} \cdot W_i, \quad (7)$$

where N_{jxi} is the capacity of the idle j -th motor, kW; ΔN_{ji} is the increment of the energy consumed by the j -th motor at increasing the weight of the belt load by 1 tonne:

$$N_1 = 63 + 0.79W, \text{ kW}; \quad (8)$$

$$N_2 = 91 + 0.37W, \text{ kW}; \quad (9)$$

and for the coefficient of the drive motors capacities ratio the regression equation is the following:

$$K_{Ni} = K_{Nxi} + \Delta K_N \cdot W_i, \quad (10)$$

where K_{Nxi} is the ratio coefficient of the capacities of the drive motors in the conveyor idle running mode; ΔK_N is the increment of the ratio coefficient of the capacities of the drive motors at increasing the weight of the load on the belt by 1 tonne:

$$K_N = 0.73 + 0.95 \cdot 10^{-3} \cdot W. \quad (11)$$

The correlation coefficients for the above-considered $N_1(W)$, $N_2(W)$, and $K_N(W)$, respectively, correspond to the following values:

$$r_{N1,W} = 0.978; r_{N2,W} = 0.956; r_{KN,W} = 0.958.$$

This confirms the linear dependencies $N_1(W)$, $N_2(W)$, and $K_N(W)$, which are close to functional. The calculated and tabulated Fisher criteria for the regression dependencies $N_{1c}(W)$, $N_{2c}(W)$, and $K_N(W)$, respectively, for 60.6 thousand measurements are as follows:

$$F_{N1,W} = 0.77 < F_{0N1,W} = 1.0;$$

$$F_{N2,W} = 0.88 < F_{0N2,W} = 1.0;$$

$$F_{KN,W} = 0.78 < F_{0KN,W} = 1.0.$$

This confirms the adequacy of the regression models $N_1(W)$, $N_2(W)$, and $K_N(W)$.

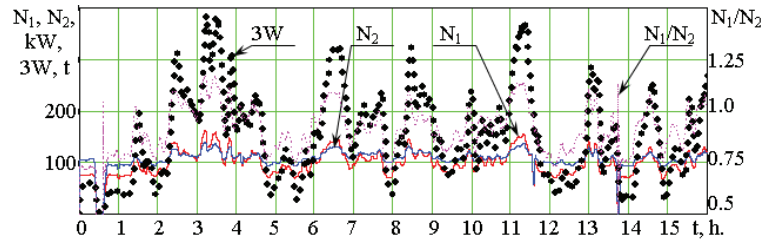


Fig. 3. Changes in the developed capacities of the drive motors N_1 (the thin red line) and N_2 (the thin blue line), the capacity ratio factor (the pink dots), and the weight of the transported load (the black marker) on the belt conveyor 2LU120V

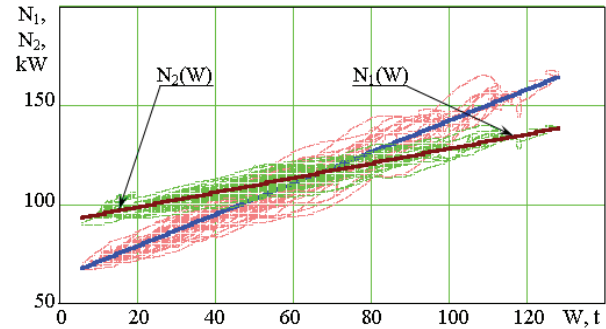


Fig. 4. The relative positions of the capacity readings of N_1 (the pink dots) and N_2 (the green dots) of the drive motors depending on the weight of the load transported by the belt, and the graphs of their regression equations (respectively, the blue and brown lines)

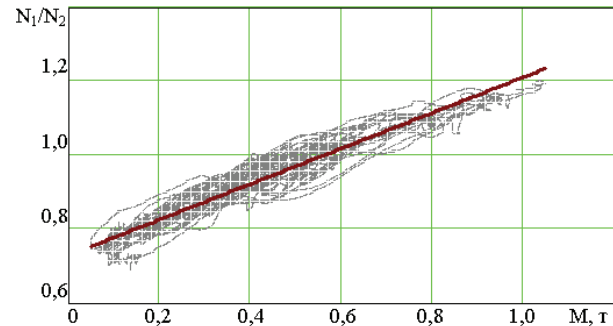


Fig. 5. The point cloud (the grey dots) and the graph (the brown line) characterizing a linear regression dependence of the capacity ratio factor of the drive motors on the relative loading of the conveyor

Thus, in real correlations, the ratio coefficient of the capacities of the drive motors K_N varies from 0.69 to 1.21, and its value essentially depends on the weight of the load transported on the conveyor belt. When the values of the

transported load weight on the conveyor belt do not exceed 70 tonnes, the capacity of the drive motor D_1 is smaller than of D_2 by 0...31 %. When the values of the transported load weight on the conveyor belt are more than 70 tonnes, the capacity of the drive motor D_1 is smaller than of D_2 by 0...21 %. Uneven loading of the drive motors adversely affects the resource of the machine. Therefore, this factor of an uneven load should be considered while creating a variable controlled drive and an intelligent system of managing a belt conveyor.

Much of the value of the capacity generated by the drive motors of a belt conveyor is determined by the distributed and lumped resistance forces taking place along the route of the conveyor. For extended conveyors, the biggest impact on the formation of the capacities of the drive motors is made by distributed resistance forces that are taken into account by the drag coefficient of the belt movement ω' . The actual value of resistance to the movement of the conveyor belt depends on the values of the operational parameters of the machine and can be determined by the experiment data. According to the methodology of calculating the proper parameters of a belt conveyor technology, the capacity of the machine that transports the load down at an angle of β is determined as follows [2]:

$$N = gkv\eta^{-1}[(W + W_0 + W_p' + W_p'')\omega' \cos\beta - W \sin\beta], kW, \quad (12)$$

where $W_0 = 64.9$ tonnes is the weight of the conveyor belt; $W_r' = 28.9$ tonnes is the weight of the rotating parts of the upper rollers of the conveyor; $W_r'' = 12.2$ tonnes is the weight of the rotating parts of the lower rollers of the conveyor; $k = 1.2$ is the factor that accounts for local resistance along the route of the belt conveyor; $\eta = 0.7...0.8$ is the efficiency factor of the electromechanical actuator.

By estimating the ratio ω' at an idle running ($W = 0$), we get:

$$\omega' = \frac{N_0\eta}{gkv(W_0 + W_p' + W_p'')\cos\beta}. \quad (13)$$

For the experimental conditions, the drag coefficient in the belt movement will be $\omega' = 0.05$, which is higher than the drag coefficient in the belt movement $\omega'' = 0.035$ that is recommended by common methods of the value calculation [2]:

$$\frac{\omega' - \omega''}{\omega'} \cdot 100\% = \frac{0.05 - 0.035}{0.05} \cdot 100\% = 30\%,$$

which indicates that there is additional resistance to the belt movement occurring due to a longer operation life of the belt conveyor. One of the reasons for increasing the drag coefficient in the belt movement is jamming of the support rollers of the machine flight.

Thus, in the experimental conditions, the drag coefficient in the conveyor belt movement exceeds the calculated value by 30 %, which should also be taken into account in the traction and energy calculations for the machine.

For assessing the uneven load flow $Q(t)$ and its effect on the nature and magnitude of changes in the transported load weight $W(t)$ and on the capacities developed by the drive motors of the conveyor $N_1(t)$ and $N_2(t)$, the above-described parameters of the conveyor operation as random processes

were evaluated by means of a correlational and spectral analysis.

The value of the normalized autocorrelation function for the time of a j -th step of a deviation $\tau_j = j \cdot \Delta t$ ($j = (0...l)$; l is the maximum number of values of the autocorrelation function) was determined by the formula:

$$C_R(\tau_j) = \frac{\sum_{i=0}^{m-j} (R_i - \bar{R})(R_{i+j} - \bar{R})}{D_R(m-j)}, \quad (14)$$

where R_i is an i -th value of a random process $R(t)$; m is the number of values of the random process $R(t)$ during its implementation; \bar{R} , and D_R are the expectation and variance of the random process $R(t)$.

The values of the normalized spectral density of the random process $R(t)$ are determined by the formula:

$$S_R(\omega_k) = \frac{\pi}{2} \sqrt{\left[\sum_{j=0}^l C_R(\tau_j) \cdot \cos(\omega_k \tau_j) \right]^2 + \left[\sum_{j=0}^l C_R(\tau_j) \cdot \sin(\omega_k \tau_j) \right]^2}, \quad (15)$$

where ω_k is the frequency of the harmonics of the random process $R(t)$.

The assumed minimum ω_{\min} was a spectrum frequency determined by the length of a random process T , namely $\omega_{\min} = 8\pi T^{-1}$; the assumed maximum ω_{\max} was a multiple step sampling of readings on the capacity of the drive motors, from tensiometers and dynamometers: $\Delta t = 1s$, — $\omega_{\max} = 20\pi \cdot (\Delta t)^{-1}$.

The magnitude of changes in the values of the range of $R(t)$ is estimated by the variation coefficient:

$$v_R = \frac{\sqrt{D_R}}{\bar{R}}. \quad (13)$$

For the correlational and spectral analysis as well as for assessing the value of the variation range of the parameters, a representative section was selected for implementing the net time of a continuous recording of the readings from tensiometers, dynamometers, and power sensors for the time duration of $T = 7.4 \text{ h} = 26.7 \cdot 10^3 \text{ s}$ of continuous work of a belt conveyor with a non-controlled drive. This corresponds to the period during which the machine is switched on — between 16:57 of 25 May 2011 and 00:22 of 26 May 2011 of the calendar time.

The nature and magnitude of changes in the load flow and the transported load weight on the belt for the chosen area is shown in Fig. 6. The normalized autocorrelation function of the load flow $C_Q(\tau_j)$ and the transported load weight $C_W(\tau_j)$, as well as the corresponding spectral densities $S_Q(\omega_k)$ and $S_W(\omega_k)$, which were calculated according to the above-suggested formulas, are shown in Fig. 7.

The analysis of these dependencies (Fig. 6) reveals a big unevenness of the load flow $Q(t)$ and the weight of the transported load on the belt $W(t)$ in the absence of regulation of the transportation speed. The uneven load flow occurs due to the technological cycle of coal extraction in the clearing and preparatory faces and the combined machine performance. The coefficients of variation of the transported load flow and weight at a constant speed of the load transportation are close, and their values are, respectively, $k_{vQ} = 0.52$ and $k_{vW} = 0.48$. The smaller value of the variation coefficient of

the transported load weight on the belt k_{vW} , in comparison with the coefficient of variation of the load flow k_{vQ} , is caused by smoothing high flow frequencies during loading the belt along the length of the conveyor ($t = 6$ min) while the transported load weight $W(t)$ is formed therein. These frequencies are caused by unevenness of the feed rate produced by the cutters-loaders, the direction of their movement (in the bidirectional mode of extraction), and the work of the down-hole and transportation equipment prior to the tests on the conveyor.

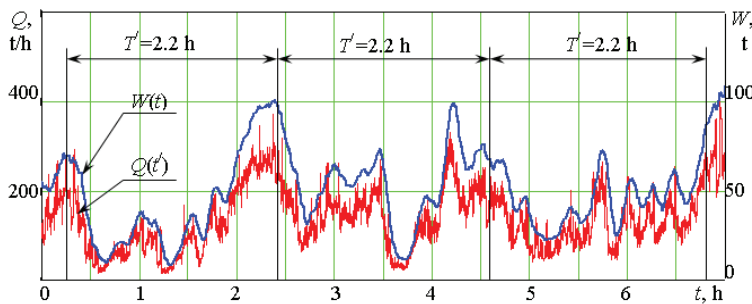


Fig. 6. Changes in the time of the load flow $Q(t')$, the red line, and the weight of the load transported on the belt $W(t)$, the blue line, during the conveyor operation from 16:57 on 25 May 2011 till 00:22 on 26 May 2011

A comparative analysis of the normalized autocorrelation functions of the load flow $C_Q(\tau_j)$ and the weight of the transported load on the belt $C_W(\tau_j)$ (Fig. 7, *a*) reveals that they are almost completely identical. These processes are characterized by the presence of random (fast fading) and periodic components. In this case, the RMS deviation in the processes $\sqrt{D_R}$ are: for the flow, $\sqrt{D_Q} = 72.7$ t/h; for the transported load weight, $\sqrt{D_W} = 23.7$ t. The periodic component, which is assessed by the autocorrelation functions that are recorded in the experiment, corresponds to the time interval $T = 2.2$ hours, which, in turn, corresponds to the average period of a maximum load flow as a result of a blending of the work cycles of two production faces and one preparatory face (Fig. 6).

The analysis of the normalized spectral densities of the load flow $S_Q(\omega_k)$ and the transported load weight $S_W(\omega_k)$ reveals that the main dispersion of the registered random processes are found mainly in the frequencies of $\omega_1 = 0.00083$ rad/s and $\omega_2 = 0.00166$ rad/s, which correspond to the oscillation periods of $T_1 = 2$ h 8 min and $T_2 = 1$ h 3 min (Fig. 7, *b*). The period T_1 is rendered as a result of registering the load flow in the experimental conditions and calculating the correlation function that corresponds to the random process; the reason for its occurrence is described above. The period T_2 corresponds to the technological cycle of intensive coal mining in the working face, and its numerical value will depend essentially on the mining technology adopted by an enterprise. The graphs (Fig. 7) show that the described frequencies account for more than 85 % of the variance of the transported load weight and more than 75 % of the load flow dispersion. The graphs of the normalized spectral densities of these processes at a constant speed of transportation, as well

as the autocorrelation functions, are almost identical, which indicates that the distribution of the process dispersions is almost the same in the relevant frequencies.

Thus, the load flow of the mined bulk during intensive coal mining in two clearing and one preparatory faces is characterized by high non-uniformity (the coefficient of variation is $k_{vQ} = 0.52$), which largely determines the type and the uneven weight of the load on the belt (the coefficient of variation is $k_{vW} = 0.48$) at an unregulated speed of the conveyor. The uneven load flow occurs due to the technological cycle of coal extraction

in the clearing and preparatory faces, the direction and the speed of the movement of combined machines (in a bidirectional mode of mining), and the test-preceding work of the downhole and transportation conveyors. The main variances of the load flow (75 %) and the transported load weight (85 %) coincide with low frequencies corresponding to the periods of $T_1 = 2$ h 8 min and $T_2 = 1$ h 3 min depending on the modes of extracting and transporting the mined bulk.

Fig. 8 shows the normalized autocorrelation functions of the capacities of the first $C_{N1}(\tau_j)$ and the second $C_{N2}(\tau_j)$ motors as well as the corresponding spectral densities $S_{N1}(\omega_k)$ and $S_{N2}(\omega_k)$.

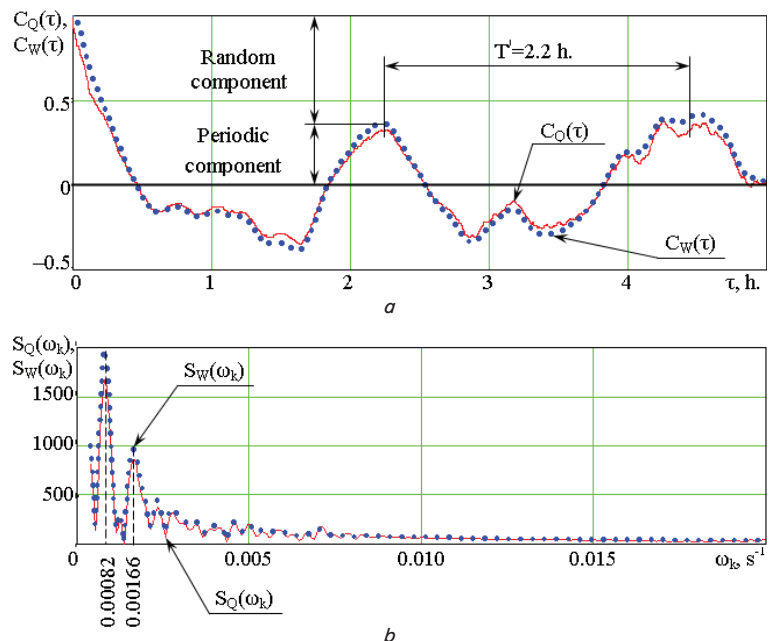


Fig. 7. The normalized autocorrelation functions of the load flow (the red line) and the weight of the transported load (the blue marker), as well as the corresponding spectral densities: *a* — the autocorrelation functions of the load flow $C_Q(\tau_j)$ and the transported load weight $C_W(\tau_j)$; *b* — the spectral densities of the load flow $S_Q(\omega_k)$ and the transported load weight $S_W(\omega_k)$

The analysis of these dependencies (Fig. 3) reveals a decrease in the unevenness of the capacities developed by the drive motors. The values of the capacity variation coefficients for the first and the second drive motors respectively constitute $k_{vN1} = 0.19$ and $k_{vN2} = 0.09$ due to the high capacity of the idle running of the belt and a redistribution of the total capacity developed by the machine between the drive motors. The coefficient of variation for the capacity of the second drive motor is 2.1 times lower than of the first drive motor. Consequently, the effect of an uneven distribution of

the transported load weight $W(t)$ on the capacity developed by the first drive motor, $N_1(t)$, is more substantial than the capacity developed by the second drive motor, $N_2(t)$.

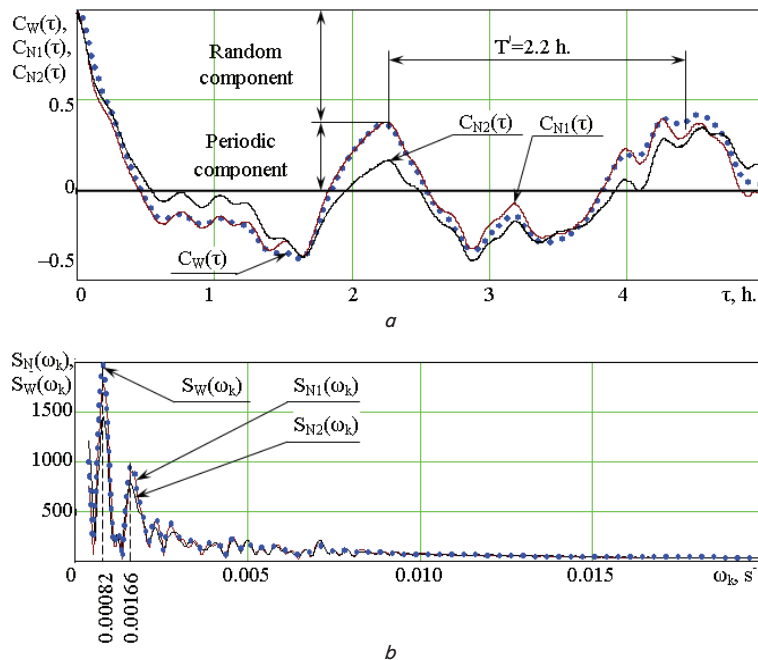


Fig. 8. The normalized autocorrelation functions of the transported load weight (the blue marker), the capacities developed by the drive motors, N_1 (the brown line) and N_2 (the black line), and the corresponding spectral densities: *a* — the autocorrelation functions of the capacities of the first $C_{N1}(\tau_i)$ and the second $C_{N2}(\tau_j)$ motors; *b* — the spectral densities of the capacities developed by the first $S_{N1}(\omega_k)$ and the second $S_{N2}(\omega_k)$ motors

The coefficients of variation for the capacities of the drive motors N_1 and N_2 , according to (12), are determined by the formulas:

$$v_{N1} = \frac{\sqrt{D_{N1}}}{N_{1x} + \bar{N}_1}, \quad v_{N2} = \frac{\sqrt{D_{N2}}}{N_{2x} + \bar{N}_2}, \quad (16)$$

where $\sqrt{D_{N1}}$ and $\sqrt{D_{N2}}$ are the standard deviations of the capacities developed by the first and the second drive motors, respectively; N_{1x} and N_{2x} are the capacities of an idle running of the first and the second drive motors, respectively, derived from the regression equations (8) and (9): $N_{1x} = 63$ kW and $N_{2x} = 91$ kW; \bar{N}_1 and \bar{N}_2 are the average increments of the capacities generated by the motors during transporting the load by the conveyor. According to the experiment results for the given implementation area, $\bar{N}_1 = 40$ kW and $\bar{N}_2 = 20$ kW.

The RMS deviation in the capacities N_1 and N_2 developed by the motors respectively constitute $\sqrt{D_{N1}} = 20$ kW and $\sqrt{D_{N2}} = 10$ kW. Consequently, $v_{N1} = 20/(63+40) = 0.19$ and $v_{N2} = 10/(91+20) = 0.09$. Excluding the idle running capacities, the values of the coefficients of variation in terms of the increments of these capacities are about $v_1 \approx v_2 \approx 0.5$, which corresponds to the values of the coefficients of variation of the load flow and the transported load weight.

The correlational and spectral analysis of the capacities developed by the drive motors confirms an impact on them made by the dispersions of low-frequency components of random processes associated with the mineral extraction

technology used by the mining enterprise. The graphs of the normalized autocorrelation functions (Fig. 8, *a*) and the spectral densities (Fig. 8, *b*) of the processes in question — respectively, $C_{N1}(\tau_j)$ and $C_{N2}(\tau_j)$ as well as $S_{N1}(\omega_k)$ and $S_{N2}(\omega_k)$ — are also almost identical. Besides, at a constant speed of the belt, there is an impact of the dispersions of these processes at the frequencies ω_1 and ω_2 , corresponding to those in the graphs of the normalized autocorrelation functions as well as the spectral densities of the load flow $Q(t)$ and the load weight transported on the belt $W(t)$. These frequencies correspond to more than 80 % of the capacity variance of the drive N_1 and to more than 70 % of the capacity variance of the drive N_2 . Therefore, while increasing the technical level of the belt conveyor for intensive coal mining, it is primarily necessary to optimize the mining technology of the enterprise. The effect of time on loading the conveyor to the capacities of the drive motors at a constant belt speed is not essential because the time of loading the conveyor ($t = 6$ min) is much shorter than the periods associated with the technological processes of mining at the enterprise in question, for they are measured in hours ($T_1 \approx 2.2$ h and $T_2 \approx 1$ h).

Thus, the correlational and spectral analysis of the capacities developed by the drive motors has revealed a significant effect of the character of changes in the load flow and the belt-transported load weight on the capacities developed by the drive motors. When the belt conveyor drive is unregulated, the unevenness of capacities of the first and the second drive motors (the variation coefficients are, respectively, $k_{vN1} = 0.19$ and $k_{vN2} = 0.09$) is less significant as compared with the unevenness of the load flow and the transported load weight due to the high capacity of the idle running of the drive motors of the tested conveyor. The influence of the uneven distribution of the transported load weight on the motor that is located in the place of the belt running off the drive is less substantial than on the motor that is located in the place of the belt running onto the drive of the conveyor. The main dispersion of the capacities of the first (85 %) and the second (75 %) drive motors, the same as the main dispersion of the load flow and the transported load weight on the belt, coincides with low frequencies corresponding to the periods of $T_1 = 2$ h 8 min and $T_2 = 1$ h 3 min, depending on the technologies of extracting and transporting the mined bulk.

Consequently, to improve the technical level of the transport machines for intensive coal mining in modern mines and to establish a constant load flow, it is advisable to create cutters-loaders with a constant productivity of extracting coal (rock). To maintain a steady weight of the load on the belt when one of the faces starts or stops working and the mined bulk comes to the assembled belt conveyor, it is advisable to regulate the speed of the conveyor belt along with the regulation of the performance of the main technological equipment. In addition, it is advisable to use other methods of balancing the load flow — for example, to use mechanized bunkers. A positive impact on energy consumption and the belt resource is made by reducing the amplitude of loading the electrical and mechanical parts of the belt conveyor.

Specific energy consumption for transporting 1 tonne of the mined bulk across a distance of 1 km on a conveyor belt will make [2]:

$$E(W_i) = \frac{N_i}{3.6vW_i} \text{ kW} \cdot \text{h}/(\text{t} \cdot \text{km}). \quad (17)$$

The weight of the load on the belt W_i corresponds to the average value of the load flow $Q_{av,i}$, which is equal to the following:

$$Q_{av,i} = \frac{3.6W_iv}{L} \text{ t/h}. \quad (18)$$

Fig. 9 shows a dependence of the relative increase in energy consumption C_e for transporting the load by a conveyor on the load factor along the length of the belt and in terms of its receiving (loading) capacity C_l .

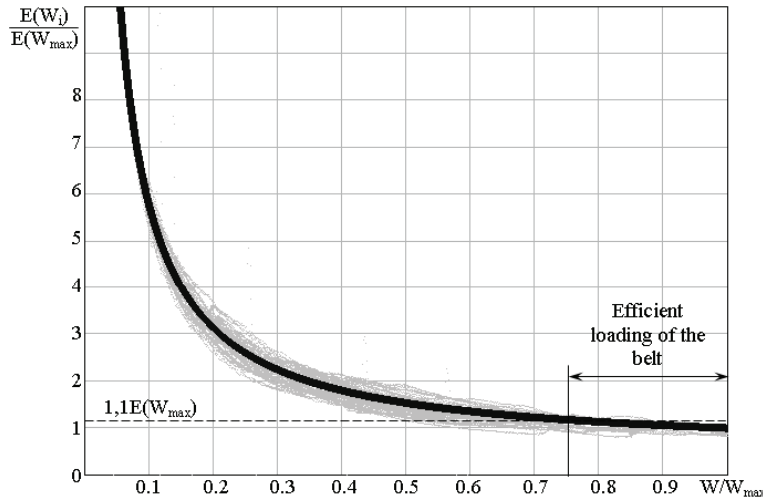


Fig. 9. The dependence of a relative increase in energy consumption for transporting the load on the factor of the belt loading along the length and in terms of the receiving capacity of the belt conveyor: the experiment data are in black dots, and there is a graph that corresponds to the formula (17)

The above-described factors are determined by the correlations:

$$C_l = \frac{W_i}{W_{max}}, \quad (19)$$

$$C_e = \frac{E(W_i)}{E(W_{max})}, \quad (20)$$

where W_{max} is the weight of the load transported on the belt and corresponding to the maximum loading capacity of the conveyor; $E(W_{max})$ is energy consumption for transporting 1 tonne of the mined bulk across a distance of 1 km, corresponding to the weight of the load W_{max} ; $E(W_i)$ is energy consumption for transporting 1 tonne of the mined bulk across a distance of 1 km, corresponding to the weight of the load W_i .

The analysis of the dependence of specific energy consumption for transporting the load by the belt conveyor reveals that when the value of the coefficient of loading the conveyor for its length and receiving capacity is $C_l = 0.75 \dots 1.0$, the ratio of the relative increase in energy con-

sumption does not exceed $C_e = 1.1$, which means that the energy loss while transporting the load will not exceed 10 % of the optimal value of energy consumption. If the value of the conveyor loading factor is $C_l = 0.5$, the coefficient of the relative increase in energy consumption is $C_e = 1.5$; at $C_l = 0.25$, $C_e = 2.6$; at $C_l = 0.1$, $C_e = 7.75$. Consequently, at $C_l < 0.75$, it is expedient to regulate the speed of the conveyor belt in order to reduce energy consumption for transportation – if it is possible to reduce the speed according to the condition of the receiving capacity of the conveyor at a variable load flow.

6. Discussion of the experiment results

The main advantage of the conducted research is that it has resulted in determining specific factors in representative conditions of intensive coal mining (in two treatment faces and one preparatory face):

- the determining influence of the type and amount of the load flow on the uneven loading of the belt when the conveyor drive is unregulated;
- a significant effect of the uneven loading of the belt on the type and unevenness of the loading of the motors, which determine the conveyor resource, and energy consumption.

The drawback of this study is a large sampling interval (1 s), which does not allow the experiment to register the high-frequency component of loading the drive motors in stationary and transient modes of the belt conveyor operation.

The obtained data can be used:

- in a conceptual development of innovative structures and highly resource-efficient transport machines of a high technical level as well as mechatronic transport systems for intensive coal mining;
- in CAD systems of conveyor transport for mining enterprises with intensive mining of mineral resources.

Directions for further research include:

- conducting a complex of studies to establish the effect of the uneven load flow and load weight distribution along the conveyor belt on the dynamic loading and resource of the elements of its design;
- justification of the structure, parameters and algorithm of an adaptive control over the operation of the belt conveyor as a mechatronic object and the conveyor lines that contain devices for stabilizing the load flows;
- justification of the space and design parameters as well as optimization criteria and the development of the objective function to optimize a belt conveyor that has a variable speed drive and conveyor lines as mechatronic systems;
- development of CAD mathematical software, taking into account the patterns determined by experimental studies, including;
- adequate mathematical models of the workflow for intensive production of a functioning belt conveyor as a mechatronic object with an adaptive drive control system;
- a mathematical model of optimizing and justifying the structure and parameters of a controlled drive and an algorithm of an adaptive belt conveyor control system for the modern mining industry.

The solution of these tasks will help solve the problem of intensifying coal mining in terms of creating reliable and effective belt conveyors of a new technological level for the mining industry. These conveyor belts, along with the diagnostics and monitoring of the equipment without disconnecting from the circuit, will have optimized energy consumption for the transportation capacity and the resource of the component parts of conveyor lines that contain devices for stabilizing load flows within a mechatronic mining production system.

7. Conclusions

1. It has been experimentally determined that in conditions of intensive coal mining the load flow of the mined bulk from several faces and the consequently formed workload of the belt of the double-drive conveyor 2LU120V have a significant impact on the loading of the drive motors and energy consumption for transporting the load. The total capacity developed by a drive of a belt conveyor at an idle running (with the weight of the load on the conveyor belt being 2...3 % of the maximum possible load of 122 tonnes) is 150...170 kW; when the conveyor starts working, it amounts to 380 kW. In the mode of transporting the load, the capacities that are developed by each driving motor vary within the range of 70 kW and 180 kW, and their ratio depends essentially on the weight of the load transported by the conveyor. The ratio of the capacities of the conveyor drive motors, characterized by the dynamic loading and the defining resource of its elements, ranges from 0.69 to 1.21. When the values of the transported load weight on the conveyor belt does not exceed 70 tonnes, the capacity of the drive motor in the place of the belt running onto the drive is 0...31 % less than of the drive motor in the place of the belt running off the drive. When the values of the transported load weight on the conveyor belt exceed 70 tonnes, the capacity of the drive motor in the place of the belt running onto the drive is 0...21 % less than of the drive motor in the place of the belt running off the drive.

2. The load flow of the mined bulk during intensive extraction of coal in two clearing faces and one preparatory face is characterized by high non-uniformity (the coefficient of variation is $v_Q = 0.52$), which largely determines the type and the uneven weight distribution of the load along the belt (the coefficient of variation is $v_W = 0.48$) at an unregulated speed of the conveyor. The uneven load flow occurs due to the technological cycle of coal extraction in the clearing and preparatory faces, the direction and speed of the movement of combined machines (in a bidirectional mode of mining), and the work of downhole and transporting conveyors preceding the tested conditions. The main variances of the load flow (75 %) and the weight of the transported load (85 %) coincide with low frequencies, which correspond to the periods of $T_1 = 2 \text{ h } 8 \text{ min}$ and $T_2 = 1 \text{ h } 3 \text{ min}$ and depend on the technologies of extracting and transport-

ing the mined bulk. When the drive of the belt conveyor is unregulated, the unevenness of the capacities of the first and the second drive motors (the variation coefficients are, respectively, $v_{N1} = 0.19$ and $v_{N2} = 0.09$) is less significant as compared with the unevenness of the load flow and the transported weight of the load due to the high capacities of the idly running drive motors of the tested conveyor. The effect of the non-uniformity of the transported load weight on the capacity developed by the drive motor that is located in the place of the belt running off the drive is less significant than the capacity generated by the motor that is located in the place of the belt running onto the drive of the conveyor. The main dispersion of the capacity of the first (85 %) and the second (75 %) drive motors, the same as the main dispersion of the load flow and the transported load weight on the belt, coincides with low frequencies corresponding to the periods of $T_1 = 2 \text{ h } 8 \text{ min}$ and $T_2 = 1 \text{ h } 3 \text{ min}$ due to the technologies of mining and transporting the mined bulk. Energy losses in an idle mode depend on the mode duration and make up 160 kW·h/hour. The minimum value of energy consumption for transporting a load by a belt conveyor corresponds to its work at full loading of the belt along the length and depending on its receiving capacity; it is 0.34 kW·h/(t·km). A reduction of the value of the load factor along the length and depending on the receiving capacity leads to a hyperbolic increase in energy consumption for transportation. When the conveyor load factor is 0.75, energy consumption for transportation increases by 10 %; if it is 0.5, the increase is by 50 %; if it is 0.25, the increase is by 160 %; if it is 0.1, the increase is by 675 %.

3. The value of the drag coefficient of the conveyor belt movement in representative conditions of intensive extraction is 0.05, which is 30 % higher than the value recommended by common methods of calculation.

4. One of the ways of increasing the efficiency of belt conveyors to intensify coal mining is to maintain the conveyor belt loading along the length and up to the receiving capacity in a given range, ensuring a maximum reduction of energy consumption for transporting the mined bulk. This is achieved by uniformity of the loading on the belt along its length and up to its receiving capacity as well as by varying the speed of the conveyor drawbar organ in case of an uneven supply of the load. To improve the technical level of transport machines for intensive coal mining in modern mines with the aim of establishing a constant load flow, it is advisable to create cutters-loaders with a steady capacity of extracting coal (rock). To maintain a stable weight of the load on the belt, when one of the supplying faces starts or stops working, it is advisable to regulate the conveyor belt speed along with the regulation of the performance of the main technological equipment and to stabilize load flows by using equipment of the transport lines. The amplitude of loading the electrical and mechanical parts of the conveyor belt can be reduced as a result of the above-described activities to have a positive impact on energy consumption and the resource of the belt conveyor.

References

1. Nikolaichuk, V. Transportable and Technological logistics in energy-intensive industries [Text] / V. Nikolaichuk, V. Budishevsky, V. Gutarevich, V. Kislun, A. Sulima; V. A. Budishevsky, A. A. Sulima (Eds.). — Donetsk, 2003.
2. Adadurov, V. Theoretical basis and calculations of transport in energy-intensive industries [Text] / V. Adadurov, V. Arinenkov, F. Voyush et. al.; V. A. Budishevsky, A. A. Sulima (Eds.). — Donetsk, 1999. — 217 p.

3. Shahmeyster, L. The dynamics of traffic and speed control of conveyor belts [Text] / L. Shahmeyster, V. Dmitriev, A. Lobacheva. — Moscow: Nedra, 1972. — 173 p.
4. Lobacheva, A. Energy performance of conveyor transport and irregular with adjustable-speed [Text] / A. Lobacheva. — Mining and quarrying transport, 1971. — P. 158–163.
5. Babockin, G. Mathematical model of the twin-engine conveyor with adjustable electric [Text] / G. Babockin, D. Shprekher // Proceedings of the V International (16th All-Russian) Conference on automated electric, 2007. — P. 365–366.
6. Korneev, S. Emergency overload of downhole scraper conveyors with hydrodynamic drive and hydraulic tensioning devices simulation [Text] / S. Korneev, V. Dobronogova, V. Safonov // Collection of scientific works of Donbass State Technical University. — 2012. — Vol. 36. — P. 35–43.
7. Osichev, A. Assessing the impact of the internal viscous friction of the traction body and scraper conveyor resistance forces its movement the dynamics of electromechanical system [Text] / A. Osichev, A. Tkachenko // Bulletin of National Technical University KhPI. — 2008. — Vol. 30. — P. 187–189.
8. Osichev, A. The development of the family computer models to study dynamical processes in electric conveyors [Text] / A. Osichev, A. Tkachenko // News M.O. strogodsky Kremenchug sovereign politechnical university. — 2008. — Vol. 3, Issue 50, Part 2. — P. 154–157.
9. Osichev, A. Evaluation of the dynamic properties of the electric scraper conveyor SR 72 at various reasons for jamming its working body [Text] / A. Osichev, A. Tkachenko. — Problems automated electric. Theory and Practice, 2009. — 516 p.
10. Zaklika, M., Kolek, M., Tytko, S. Belt conveyors with adjustable speed [Electronic resource] / M. Zaklika, M. Kolek, S. Tytko. — Available at: <http://www.bartec-russia.ru/files/mining/for-conveyance.pdf>
11. Ivantsov, V. Energy-saving soft starter and regulation of the conveyor speed [Electronic resource] / V. Ivantsov. — Available at: <http://www.erasib.ru/articles/conveyor-eraton-fr>
12. Lauhoff, H. Is the speed of belt conveyors regulation contributes to energy savings? [Text] / H. Lauhoff // Glukauf. — 2006. — Vol. 1. — P. 9–16.
13. Wheeler, C. A. Evolutionary Belt Conveyor Design — Optimizing Coasts [Text] / C. A. Wheeler. — Bulk Material Handling by Conveyor Belt. 7, Littleton, Colorado, 2008. — 108 p.
14. Prokuda, V. Research and evaluation of freight traffic on the main conveyor transport the CAP «Mine «Pavlogradska» [Text] / V. Prokuda, Yu. Mishansky, S. Protsenko // Public company DTEK «Pavlogradugol» Mining electrician. — 2012. — Vol. 88. — P. 107–111.
15. Kondrakhin, V. Traffic measurement on the belt conveyor through removable tensor device with belt tension accounting [Text] / V. Kondrakhin, N. Stadnik, P. Belitskii // DonNTU scientific works, electromechanical series. — 2013. — Vol. 1. — P. 79–87.
16. Kondrahin, V. Operating parameters statistical analysis for the belt conveyor in mine [Text] / V. Kondrahin, N. Stadnik, P. Belitskii // DonNTU scientific works, electromechanical series. — 2013. — Vol. 2. — P. 140–150.